

2D to 1D magnetic interactions evolution in $\text{Cu}_2\text{F}_{5-x}$ through electron doping by fluoride non-stoichiometry

Dmitry M. Korotin,^{1,*} Dmitry Y. Novoselov,^{1,2} and Vladimir I. Anisimov^{1,2}

¹*M.N. Mikheev Institute of Metal Physics of Ural Branch of Russian Academy of Sciences,
18 S. Kovalevskaya St., Yekaterinburg, 620137, Russia.*

²*Department of Theoretical Physics and Applied Mathematics,
Ural Federal University, 19 Mira St., Yekaterinburg 620002, Russia*

(Dated: January 3, 2023)

The copper fluoride Cu_2F_5 is a compound with 2D-magnetic exchange interactions between the Cu ions in the $S = 1$ and $S = \frac{1}{2}$ spin-states. Using *ab-initio* calculations, we predict that the existence of 5% vacancies in the fluoride sublattice of Cu_2F_5 results in the drastic transformation of the spin-state of all copper ions and the final spin-states are $S = \frac{1}{2}$ and $S = 0$. Consequently, the anisotropy of magnetic interactions increases, and the 1D linear chains of the Cu d^9 , $S = \frac{1}{2}$ ions appear. We also propose a microscopic mechanism of such exchange interaction transformation via CuO_6 octahedra elongation.

I. INTRODUCTION

Cuprates are well-known objects for the low-dimensional magnetism appearance. With such structural building blocks as CuO_6 octahedra and CuO_4 plaquettes, and due to the presence of copper ion in d^9 electronic configuration, there is a variety of magnetic structures. In perovskite-like KCuF_3 [1, 2], which structure is formed with corner-sharing CuF_6 octahedra, there is the G-type antiferromagnetic ordering of moments with existence of 1D magnetic chains of Cu ions. 2D antiferromagnetic ladders are realized in $\text{Sr}_{n-1}\text{Cu}_{n+1}\text{O}_{2n}$ [3] and SrCu_2O_3 [4] with edge-sharing CuO_4 plaquettes. And the corner-sharing plaquettes in Sr_2CuO_4 [5] and AgCuVO_4 [6] led to appearance of the one-dimensional chain of $S = \frac{1}{2}$ Cu ions.

The plethora of spin lattices mentioned above exist in the copper-oxygen complexes. The stability of the copper-fluoride complex, Cu_2F_5 , was predicted recently [7]. Structurally it is formed by both blocks: the octahedra (CuF_6) and the plaquettes (CuF_4). Consequently, one can expect that the magnetic anisotropy, similar to the one seen in the cuprates, could appear in the fluoride with or without additional doping with carriers. In our previous work [8], within the DFT+U calculations, we show that in stoichiometric Cu_2F_5 , the Cu ions are in the $S = 1$ and $S = \frac{1}{2}$ spin-states (d^8 and d^9 electronic configuration). Additionally, we obtained that the Heisenberg exchange interaction along the a crystal axis is tiny. In the (100)-plane there is antiferromagnetic superexchange between the half-filled d -orbitals of the nearest Cu ions through fluoride p -states located in between. As a consequence, the 2D spin-lattice exists in stoichiometric Cu_2F_5 .

One can assume that if an extra electron occupies the half-filled d -orbital of Cu ion in Cu_2F_5 , the corresponding Cu- $d \leftrightarrow$ F- $p \leftrightarrow$ Cu- d superexchange interaction will be

destroyed. More extra electrons will cause a significant modification of the exchange interactions. Our purpose was to find conditions under which the one-dimensional magnetic interactions prevail in copper fluoride.

We have produced additional electrons in the cell considering the doped compound – $\text{Cu}_2\text{F}_{5-x}$. Each fluoride vacancy results in an extra electron that occupies one of the copper d -orbitals. As is shown in the following sections, not only electronic and magnetic, but the crystal structure of the compound also evolves following the doping.

II. METHODS

In this paper, we follow the methodology defined in the previous one, describing Cu_2F_5 [8]. All calculations were performed using Quantum-ESPRESSO [9] package with pseudopotentials from pslibrary set [10]. The exchange-correlation functional was chosen to be in Perdew-Burke-Ernzerhof [11] form. The energy cutoff for plane wave wave functions and charge density expansion was set to 50 Ry and 400 Ry, respectively. Integration in the reciprocal space was done on a regular $8 \times 8 \times 8$ k -points mesh in the irreducible part of the Brillouin zone.

Electronic correlations were treated within the DFT+U method [12] with the Hubbard U value equals 6 eV. As it was shown for the parent compound Cu_2F_5 , even the U value of 4 eV is enough for the band gap to appear. The variation of the U from 4 to 8 eV doesn't change the electronic structure qualitatively and affects the Heisenberg exchange interaction parameters only slightly. The Hund parameter $J = 0.9$ eV was set to its typical value for cuprates [13, 14].

The convergence criteria used for crystal cell relaxation within DFT+U are: total energy $< 10^{-6}$ Ry, total force $< 10^{-3}$ Ry/Bohr, pressure < 0.1 kbar.

* dmitry@korotin.name

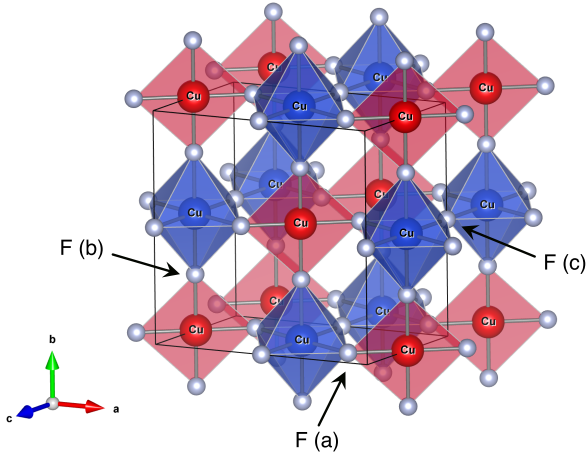


FIG. 1. Crystal structure of Cu_2F_5 and the three types of fluoride ions that were removed to obtain the structure of $\text{Cu}_2\text{F}_{5-x}$. Blue spheres denote Cu ions inside the ligand's octahedron, red spheres denote Cu ions in the center of plaquettes, and gray spheres – F ions. Visualized using VESTA [15].

III. RESULTS

There are three different structural sites for the fluoride ion in Cu_2F_5 that could be substituted by a vacancy: (a) the fluoride shared by CuF_4 plaquette and CuF_6 octahedron that are placed along the a axis of the cell; (b) the ion shared by CuF_4 plaquette and CuF_6 octahedron in the direction of the b axis; (c) the fluoride belonging to the two CuF_6 octahedra along the c axis. The Cu-F-Cu bond angle is 180 degrees for the (b) and (c) ions and only 129 degrees for the case-(a) fluoride ion, which results in much weaker magnetic exchange interaction in the direction of the a axis. The absence of one of these F-ions would naturally lead to a change in the electronic configuration of the nearest Cu ions. With the destruction of the Cu-F-Cu superexchange path, the disappearance of one fluoride ion probably will change the magnetic exchange interaction pattern in Cu_2F_5 .

In the Cu_2F_5 crystal cell containing 8 Cu ions (see Fig. 1), we removed the F ion in (a), (b), or (c) position sequentially, as described above, and performed full cell relaxation within the DFT+U approach to obtain a ground state crystal structure. The used cell size corresponds to a 5% concentration of fluoride vacancies ($\text{Cu}_2\text{F}_{4.75}$), and we are focused on this simplest and the most visual case.

After the relaxation, we compared the enthalpies of the obtained structures. The lowest enthalpy has the cell where the vacancy is placed instead of the F ion in the (b) position. If F is removed from the (c) position, the enthalpy is +45 meV / formula unit higher and it is +46 meV/formula unit higher for the vacancy in the (a) position. We conclude that the favorable vacancy localization site in Cu_2F_5 is the F ion shared by CuF_4

Parameter	Cu_2F_5	$\text{Cu}_2\text{F}_{4.75}$
Cell volume (\AA^3)	369.3	393.6
$\text{Cu}_{\text{octa}} - \text{Cu}_{\text{octa}}$ distance along a (\AA)	6.98	6.96
$\text{Cu}_{\text{octa}} - \text{Cu}_{\text{octa}}$ distance along b (\AA)	7.61	8.08
$\text{Cu}_{\text{octa}} - \text{Cu}_{\text{octa}}$ distance along c (\AA)	7.60	7.52
Average $\text{Cu}_{\text{plaq}}-\text{F}$ bond length (\AA)	1.90	1.80
Average $\text{Cu}_{\text{octa}}-\text{F}$ bond length (\AA)	1.93	2.04
Average $\text{Cu}_{\text{octa}}-\text{F}$ distance along b (\AA)	1.93	2.26

TABLE I. Transformation of crystal structure of Cu_2F_5 with electrons doping via vacancies.

plaquette and CuF_6 octahedron in the direction of the b axis. Below under the $\text{Cu}_2\text{F}_{4.75}$ or $\text{Cu}_2\text{F}_{5-x}$, we mean the corresponding crystal structure.

The vacancy creation results in the crystal structure distortions presented in Table I. The unit cell volume increase of 6.6% happens from the elongation of the cell along the b lattice vector. At the same time, there is an expansion of the CuF_6 octahedra and a decrease of the average Cu-F bond length within the CuF_4 plaquette in $\text{Cu}_2\text{F}_{5-x}$.

The two Cu ions, that had the F ion in between in Cu_2F_5 , and have the vacancy site instead in $\text{Cu}_2\text{F}_{4.75}$, are slightly shifted to each other along the b crystal axis. Hereafter, the Cu-F bonds of the $ex-\text{CuF}_4$ plaquette and the $ex-\text{CuF}_6$ octahedron are distorted when they lose the shared fluorine ion. For the next-nearest to the vacancy Cu-F octahedra and plaquettes, one can still say that the local environment for the Cu ion remains an octahedron and a plaquette. The structure files for Cu_2F_5 and $\text{Cu}_2\text{F}_{4.75}$ could be found here [16].

The $\text{Cu}_2\text{F}_{4.75}$ is an antiferromagnetic insulator with a 0.91 eV band gap. The calculated partial densities of states (pDOS) are presented in Fig. 2. A plausible assumption would be to say that all copper ions inside the fluoride octahedra have very similar pDOSes despite the various distortions of CuF_6 structures regarding the distance from the vacancy. The same is true for the CuF_4 plaquettes. The corresponding pDOSes are marked in Fig. 2 as Cu_{octa} and Cu_{plaq} respectively. Here and below, we refer to the Cu $3z^2 - r^2$, $x^2 - y^2$, etc. orbitals in terms of the local coordinate system for each Cu ion, with the z direction is perpendicular to the plaquette plane for the Cu_{plaq} ion and the z direction is along with the crystal b vector for the Cu_{octa} ion.

From the analysis of pDOS, one can see that Cu ions in the octahedral environment obtained an additional electron and became Cu^{2+} ions in d^9 , $S = \frac{1}{2}$ electronic configuration: all t_{2g} and $3z^2 - r^2$ orbitals are filled, and the $x^2 - y^2$ orbital is half-filled. At the same time, the plaquette-surrounded Cu ions are now in d^8 , $S = 0$ configuration and have negligible magnetic moments. Both $\text{Cu}_{\text{ex-plaq}}$ and $\text{Cu}_{\text{ex-octa}}$ ions are in d^9 , $S = \frac{1}{2}$ electronic configuration with the hole at the $x^2 - y^2$ orbital. We started our calculation from the cell containing 4 Cu_{octa} ions in d^8 , $S = 1$ configuration + 4 Cu_{plaq} ions in d^9 ,

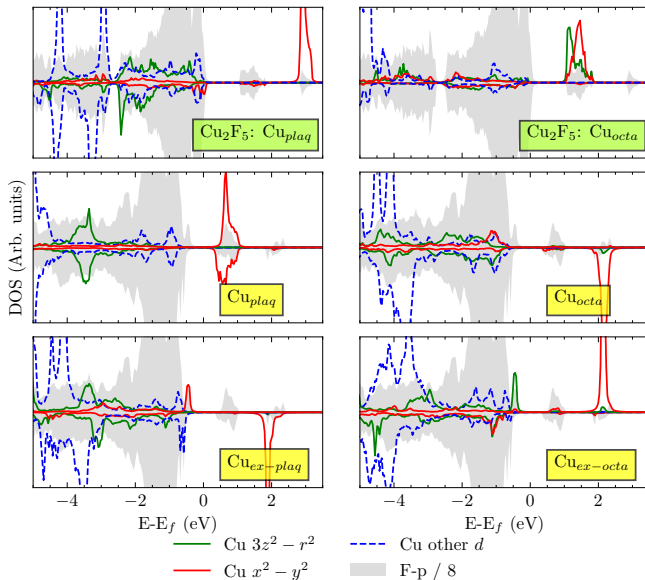


FIG. 2. Partial densities of states for Cu_2F_5 (upper panel) and $\text{Cu}_2\text{F}_{5-x}$ (middle and lower panels). Positive/negative pDOSes correspond to spin-up/down states respectively.

$S = \frac{1}{2}$ configuration + an electron from the vacancy. At the end we've obtained 3 Cu_{plaq} ions in d^8 , $S = 0 + 5$ Cu ions (3 Cu_{octa} , $\text{Cu}_{\text{ex-plaq}}$, $\text{Cu}_{\text{ex-octa}}$) in d^9 , $S = \frac{1}{2}$ configuration.

In the Cu_2F_5 [8] the lower unoccupied state is the $3z^2 - r^2$ orbital of the Cu_{octa} ions (Fig. 2, upper panel, right graph). We assumed that as a consequence of the doping, the additional electron will occupy some of these orbitals. Consequently, metallization of the Cu_2F_5 with electron doping was expected due to the appearance of the partially filled Cu_{octa} $3z^2 - r^2$ states. Surprisingly we observe an electron transfer from the Cu_{plaq} ions to the Cu_{octa} ions in Cu_2F_5 with doping. We interpret it in the following way. Due to the partial occupation of the Cu_{octa} $3z^2 - r^2$ orbital, the corresponding octahedron elongates in the c direction, that results in the expansion of the cell along the c axis. Consequently, all the CuF_6 octahedra are elongated. Since the Cu-F distances in the b direction within the octahedron become large, the Cu_{octa} $3z^2 - r^2$ orbital turns energetically more favorable than even the Cu_{plaq} $x^2 - y^2$ orbital. Electrons that occupied the Cu_{plaq} $x^2 - y^2$ state in the stoichiometric Cu_2F_5 leave it in $\text{Cu}_2\text{F}_{5-x}$ and fill the Cu_{octa} ions d-shell. As a result, Cu_{plaq} ions that have the d^9 configuration in Cu_2F_5 , become d^8 in the doped structure, and Cu_{octa} ions change their configuration in reverse way.

To confirm such evolution of crystal and electronic structure arises from the electronic degrees of freedom, not from interactions between the vacancy states, we modeled the electrons doping in a stoichiometric Cu_2F_5 . The fluoride ion wasn't removed. We just added one extra electron in the cell and relaxed the crystal structure.

As a result, the same effect was qualitatively repro-

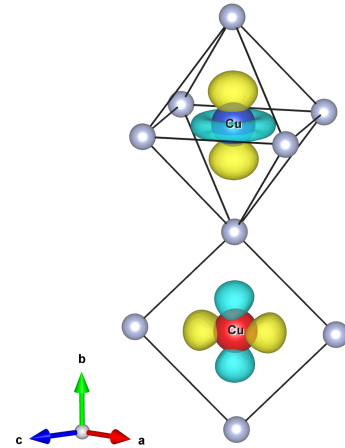


FIG. 3. Two half-filled d -orbitals of Cu ions that provide the superexchange interaction via F p -orbital along the b axis in stoichiometric Cu_2F_5 . In $\text{Cu}_2\text{F}_{5-x}$ the $d_{3z^2-r^2}$ become fully filled and the superexchange is suppressed.

duced. The cell volume increase by 17.5% with its significant elongation along b direction ($\text{Cu}_{\text{octa}}\text{-Cu}_{\text{octa}}$ distance grows up to 8.08 Å). The CuF_6 octahedra are stretched along b direction too, with the corresponding average $\text{Cu}_{\text{octa}}\text{-F}$ bond length equals 2.25 Å. The spin-state of the copper ions was also changed as a result of the existence of additional electrons: the Cu_{octa} ions became d^9 , $S = \frac{1}{2}$.

We concluded that the electronic configuration and spin state of the copper ions in Cu_2F_5 evolve in the same manner if an extra electron appears regardless of the origin of the extra electron (vacancy or manual increase in the number of carriers within the cell). We continue our presentation and reasoning below for $\text{Cu}_2\text{F}_{5-x}$ with the vacancy.

The half-filled $d_{3z^2-r^2}$ -orbital of Cu_{octa} ions in Cu_2F_5 gives the superexchange interaction path between Cu_{octa} and Cu_{plaq} ions along the b crystal axis as it is shown in Figure 3. The electrons hopping between Cu_{octa} $d_{3z^2-r^2}$ and Cu_{plaq} $d_{x^2-y^2}$ via the F- p orbital in between led to the antiferromagnetic exchange. In $\text{Cu}_2\text{F}_{5-x}$ the possibility of such a hopping of electrons is suppressed, since Cu_{octa} $d_{3z^2-r^2}$ becomes filled. Consequently, the corresponding superexchange interaction along the b crystal axis vanishes.

The described evolution of electronic structure has an outcome that the 1D chains of Cu_{octa} ions with a hole on the $d_{x^2-y^2}$ -orbital appear. Taking into account the existence of the fluoride ion between such copper ions and following the Goodenough-Kanamori rule [17], the antiferromagnetic superexchange interaction will emerge along the c crystal axis.

Using Green's function method based on magnetic-force linear response theory [2], we computed the Heisenberg exchange interaction between Cu ions up to the 9th

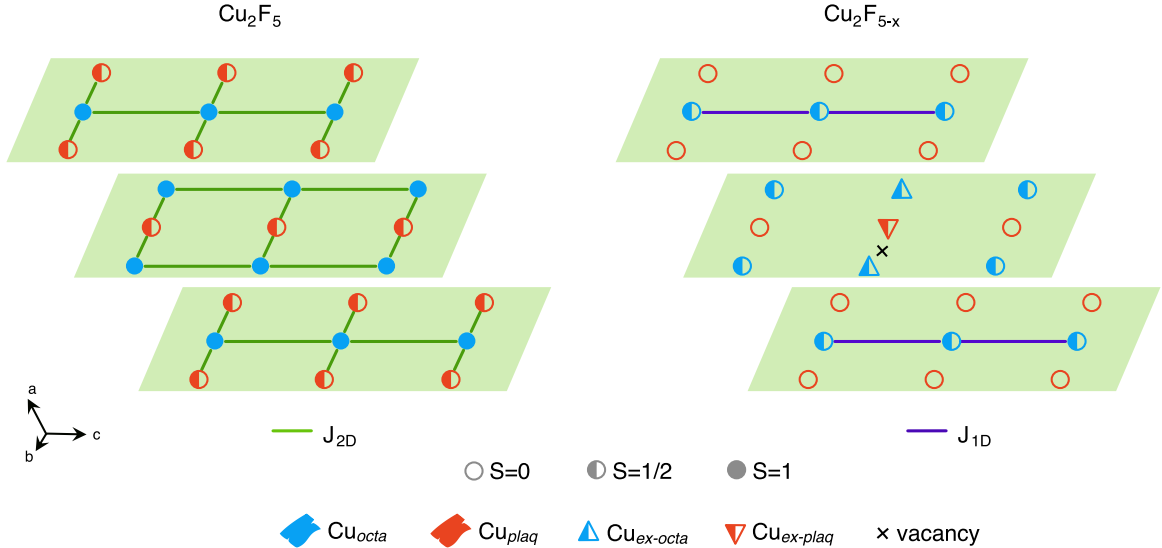


FIG. 4. Evolution of spin-states and patterns of the exchange interaction between the Cu ion from Cu_2F_5 (left) to $\text{Cu}_2\text{F}_{5-x}$ (right). Blue elements denote Cu ions in the octahedral surrounding, red elements denote Cu ions in the center of fluoride plaquettes. The blue and red half-filled triangles correspond to $\text{Cu}_{ex-octa}$, $S = \frac{1}{2}$ and $\text{Cu}_{ex-plaq}$, $S = \frac{1}{2}$ ions respectively. The filled, half-filled and empty circles denote $S = 1$, $S = \frac{1}{2}$, and $S = 0$ spin-states of the ions. The (100) lattice planes are shown with a light green color for an eye guide. The vacancy position is shown with a black cross. The strongest exchange interactions are J_{2D} in Cu_2F_5 (green line) and J_{1D} in $\text{Cu}_2\text{F}_{5-x}$ (violet line). Other exchange interactions are negligible. Fluorine ions are not shown for clarity.

nearest neighbor. The model Hamiltonian has the form: $H = -\sum_{\langle ij \rangle} J_{ij} \mathbf{e}_i \cdot \mathbf{e}_j$, where \mathbf{e}_i are the unit vectors pointing in the direction of the i th site magnetization, and the summation runs once over each ion pair.

Only one exchange interaction survived under doping. The antiferromagnetic exchange between the Cu_{octa} ions along the c -axis is $J_{1D} = -29.5$ meV. The second largest interaction ≈ -3.3 meV is between Cu_{octa} and $\text{Cu}_{ex-plaq}$ ions along the [101]-direction. The pattern of the 1D magnetic chains stems from such exchanges with the interchain interaction being an order of magnitude smaller than the intrachain one. It is shown in Fig. 4, right panel. The figure illustrates also the evolution of the strongest exchange interactions in Cu_2F_5 that arose from electron doping. The absolute value of the exchange remains almost the same: $J_{2D} \approx -33$ meV in Cu_2F_5 , but the dimension of the interaction decreases from 2D to 1D as a result of doping.

We point here to an analogy to the exchange interaction pattern that exists in KCuF_3 . The potassium copper fluoride is formed with the CuF_6 octahedra, and all copper ions have a hole on the $d_{x^2-y^2}$ orbital [14]. Since there is the Jahn-Teller distortions of the octahedra, the lobes of the half-empty d -orbitals of the nearest Cu ions are perpendicular to each other in the [001]-plane. Consequently, the superexchange via the F p -orbitals in the [001]-plane is negligible in KCuF_3 and the 1D chains of antiferromagnetically ordered moments appear along the c crystal axis. Therefore, despite the different building

blocks of the structure in $\text{Cu}_2\text{F}_{5-x}$ (octahedra and plaquettes) and KCuF_3 (octahedra only), there is a similarity in the magnetic interactions picture between these two compounds.

IV. CONCLUSION

Using the DFT+U calculations, we explored the influence of the fluoride vacancy appearance on the crystal, electronic and magnetic structure of $\text{Cu}_2\text{F}_{5-x}$. Extra electrons, which resulted from the absence of the fluorine ion, are shown to result in the elongation of the CuF_6 octahedra along the b crystal axis and then the $3z^2 - r^2$ orbital of all Cu_{octa} ions becomes occupied. As a result, all the Cu ions in the center of CuF_6 octahedra get $S = \frac{1}{2}$ spin configuration, and the Cu ions inside the CuF_4 plaquettes become non-magnetic ($S = 0$). Such significant effect become apparent even when one extra electron per 4x formula unit is added. The antiferromagnetic linear chains of copper ions appear along the c -axis of the crystal. The interchain exchange interaction is ten times smaller than the largest intrachain one. Our calculations show consistently that $\text{Cu}_2\text{F}_{5-x}$ can be described as a quasi-one-dimensional $S = \frac{1}{2}$ Heisenberg chain in a good approximation.

ACKNOWLEDGMENTS

Calculation of the ground state crystal structure for the doped $\text{Cu}_2\text{F}_{5-x}$ was carried out within the state

assignment of Ministry of Science and Higher Education of the Russian Federation (theme “Electron” No. 122021000039-4). Results on the spin-lattice evolution with doping were obtained with the support of the Russian Science Foundation (project No. 19-12-00012).

-
- [1] A. I. Liechtenstein, V. I. Anisimov, and J. Zaanen, *Phys. Rev. B* **52**, R5467 (1995).
- [2] D. M. Korotin, V. V. Mazurenko, V. I. Anisimov, and S. V. Streltsov, *Physical Review B* **91**, 224405 (2015).
- [3] S. Gopalan, T. M. Rice, and M. Sigrist, *Physical Review B* **49**, 8901 (1994).
- [4] T. F. A. Müller, V. Anisimov, T. M. Rice, I. Dasgupta, and T. Saha-Dasgupta, *Physical Review B* **57**, R12655 (1998).
- [5] H. Rosner, H. Eschrig, R. Hayn, S.-L. Drechsler, and J. Málek, *Phys. Rev. B* **56**, 3402 (1997).
- [6] A. Möller, M. Schmitt, W. Schnelle, T. Förster, and H. Rosner, *Phys. Rev. B* **80**, 125106 (2009).
- [7] N. Rybin, D. Y. Novoselov, D. M. Korotin, V. I. Anisimov, and A. R. Oganov, *Phys. Chem. Chem. Phys.* **23**, 15989 (2021).
- [8] D. M. Korotin, D. Y. Novoselov, V. I. Anisimov, and A. R. Oganov, *Physical Review B* **104**, 064410 (2021).
- [9] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari, and R. M. Wentzcovitch, *Journal of Physics: Condensed Matter* **21**, 395502 (2009).
- [10] A. Dal Corso, *Computational Materials Science* **95**, 337 (2014).
- [11] J. P. Perdew, K. Burke, and M. Ernzerhof, *Physical Review Letters* **77**, 3865 (1996).
- [12] M. Cococcioni and S. de Gironcoli, *Phys. Rev. B* **71**, 035105 (2005).
- [13] P. Blaha, K. Schwarz, and P. Novák, *International Journal of Quantum Chemistry* **101**, 550 (2005).
- [14] I. Leonov, N. Binggeli, D. Korotin, V. I. Anisimov, N. Stojić, and D. Vollhardt, *Physical Review Letters* **101**, 096405 (2008).
- [15] K. Momma and F. Izumi, *Journal of Applied Crystallography* **44**, 1272 (2011).
- [16] D. Korotin, “Crystal structure of the $\text{Cu}_2\text{F}_{4.75}$ and Cu_2F_5 copper fluorides,” *Mendeley Data*, V1, doi: 10.17632/xs2wywd7kd.1 (2022).
- [17] J. Goodenough, *Scholarpedia* **3**, 7382 (2008).