


H/D isotope effects in the electrical conductivity of LaScO₃-based solid state proton-conducting electrolyte

Ekaterina Antonova^{a*}

Received: 9 August 2024
Accepted: 20 September 2024
Published online: 20 September 2024

DOI: [10.15826/elmattech.2024.3.042](https://doi.org/10.15826/elmattech.2024.3.042)

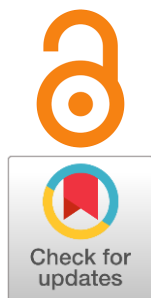

Electrical conductivity of a solid proton-conducting electrolyte with the composition of La_{0.9}Sr_{0.1}ScO₃ is studied depending on temperature and oxygen partial pressure in the atmospheres, humidified with H₂O and D₂O. Isotope H/D effect in the electrical conductivity is observed at the temperatures below 700 °C in air conditions. For reductive atmosphere, the isotope effect is pronounced for the whole investigated temperature range. Based on the *p*O₂-dependencies of electrical conductivity, the transport numbers of ions and electron holes are determined. The ionic transport numbers in the H₂O-containing atmosphere are found to be higher than the corresponding values for the D₂O-containing atmosphere for all investigated conditions. The possible role of protons (deuterons) in the oxygen ion transport is pointed out. The kinetic isotope effect is found to be predominant in the conditions under study.


keywords: LaScO₃, proton-conducting oxide, electrical conductivity, isotope H/D effect, transport number

© 2024, the Authors. This article is published in open access under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).

1. Introduction

In recent decades, perovskite-structured oxides have attracted the attention of the researchers due to various possible applications, such as ferroelectricity, luminescence, photocatalysis, fuel cells [1–3]. Among them, energy applications, for example the creation of solid oxide fuel cells (SOFCs), are of great interest in view of the increasing demand in the electricity and environmental issues [4, 5]. SOFCs are electrochemical devices, which can directly convert energy of chemical reaction to electricity. The heart of the device is a combination of a solid electrolyte and electrodes. Oxygen-ion conducting electrolytes are usually applied in conventional SOFCs (O^{2–}-SOFCs). However, some acceptor-doped ABO₃ oxides are known to dissolve water in their structure in water/hydrogen-containing

atmospheres and thus to exhibit proton conductivity according to



These materials are considered as solid proton conducting electrolytes for applications in solid oxide fuel cells, electrolysis, hydrogen sensors, etc. [6–8]. SOFCs based on solid state proton conductors (H⁺-SOFCs) have a number of advantages over O^{2–}-SOFCs, such as a lower operating temperature and the absence of fuel dilution. Currently, a wide row of perovskite-structured oxides is known to exhibit proton conductivity, e.g. solid solutions based on cerates and zirconates of alkaline-earth elements [9–15]. LaScO₃ based oxides are also typical representatives of this class of materials, combining a sufficient level of ionic conductivity with the chemical stability in the H₂O/CO₂-containing atmosphere, making them promising materials for practical application [16–18]. To date, various doping in *A*- and *B*-sublattices in LaScO₃ has already been studied, and it was found that the LaScO₃ doped with strontium in *A*-sublattice has the best

^a: Institute of High-Temperature Electrochemistry, Ekaterinburg 620066, Russian Federation

* Corresponding author: antonova_ek@list.ru

characteristics, in particular, 10 % of strontium was found to be the best level of doping [19–21].

As was mentioned above, protons appear in the crystal structure as a result of the interaction with water. Since hydrogen has a stable isotope with twice the mass - deuterium, it is possible to substitute hydrogen with deuterium in the proton-conducting oxide thus affecting its physicochemical properties, in particular, electrical conductivity [22–24]. This phenomenon is known as H/D isotope effect. Usually, the conductivity of proton conductors in the D₂O-containing atmosphere is lower than in the H₂O-containing atmosphere due to the lower mobility of deuterons than of protons (the so-called kinetic isotope effect) [25]. However, the solubility of deuterons in the oxides is shown to be higher than the solubility of protons, leading to higher concentrations of charge carriers in the first case. This effect is called the thermodynamic isotope effect and is usually more pronounced at low temperatures, when the full saturation of the oxides occurs [26, 27]. Investigation of isotope effects can be used as the verification of the proton conduction as well as give information on the mechanisms of proton conductivity [28, 29].

This paper is focused on the study of electrical conductivity of Sr-doped LaScO₃ from the point of possible H/D isotope effects.

2. Experimental

La_{0.9}Sr_{0.1}ScO₃ oxide (hereinafter LSS) was prepared by coprecipitation of the lanthanum and scandium hydroxides with further addition of strontium carbonate. La(NO₃)₃ · 6H₂O, Sc(NO₃)₃ · 4H₂O, SrCO₃ were used as starting reagents. Details of the synthesis procedure can be found elsewhere [30]. Phase purity of the resulting ceramics was confirmed by X-ray diffraction method (D/MAX-2200 RIGAKU conventional diffractometer in Cu K_α radiation ($\lambda(K_{\alpha_1}) = 1.54 \text{ \AA}$). The obtained LSS oxide was found to be single-phase, crystallizing in the perovskite structure with orthorhombic distortions, space group *Pnma*, see Figure 1. Relative density of the resulting ceramics estimated from geometrical parameters was of about 92 %.

For electrical measurements, Pt electrodes were applied on the electrolyte disk with subsequent heat treatment at 950 °C for 2 h. Electrical conductivity was measured by means of impedance spectroscopy using the IM6 (Zahner) in the temperature range of 400–800 °C in the atmosphere, humidified with H₂O or D₂O. For humidification, the gas circulating in the experimental setup was bubbled through distilled water at room temperature. Before replacing H₂O with D₂O, the gas was

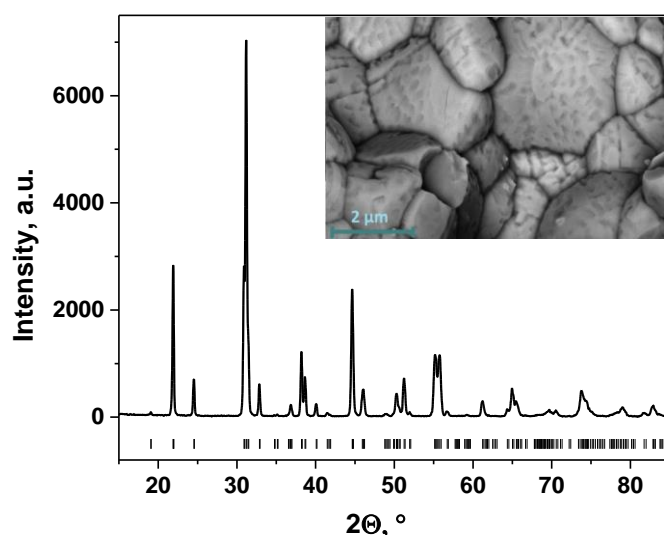


Figure 1 XRD pattern for LSS sample. On the insert – SEM image of LSS ceramics.

dried by passing through zeolites. Additionally, pO_2 -dependencies of electrical conductivity were measured in the temperature range 500–800 °C in the oxygen partial pressure range 0.21–10⁻²⁰ atm in the D₂O-containing atmosphere. Regulation of oxygen partial pressure in the experimental setup was performed using a Zirconia 318 universal controller (Russia). Impedance spectra were collected in the frequency range of 1–10⁵ Hz at the AC amplitude of 20 mV.

3. Results and discussion

Figure 2 presents temperature dependencies of electrical conductivity for LSS in air and reductive conditions, humidified with H₂O or D₂O. One can see that in air conditions the conductivity values at high temperature are almost the same for both atmospheres at the temperatures 700–800 °C, while at lower temperatures the conductivity values in H₂O-containing atmosphere exceed corresponding values in D₂O-containing one. The ratio of $\sigma(H_2O)/\sigma(D_2O)$ can be found in Table 1. The difference increases with the temperature decrease. The dependencies in air are linear, activation energy values were found to be 51 ± 3 and 57 ± 1 kJ/mol for H₂O- and D₂O-humidified air respectively. In air conditions, LSS is known to exhibit mixed ionic-electron hole conductivity, whereas under reductive conditions it is a pure ionic conductor [16, 30]. Thus, the great contribution of electron hole conductivity at high temperatures may be the reason why the isotope effect is not observed at high temperatures. Additionally, the ratio of ionic conductivities in H₂O- and D₂O-containing atmosphere ($\sigma_{ion}(H_2O)/\sigma_{ion}(D_2O)$) can be calculated. The obtained values are presented in Table 1. Basbus et al. [31] previously distinguished the electrical conductivity

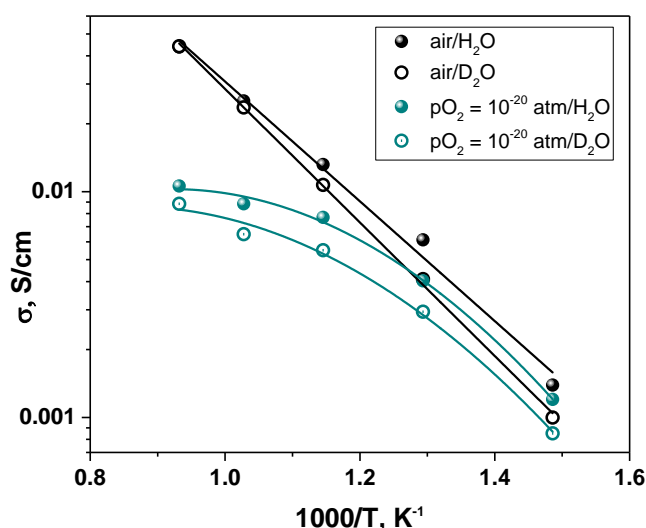


Figure 2 Temperature dependencies of electrical conductivity for LSS in air and reductive atmospheres, humidified with H₂O and D₂O.

Table 1 – Ratio of electrical conductivity values for LSS in air and under reductive conditions, humidified with H₂O and D₂O.

$T, ^\circ\text{C}$	$\sigma(\text{H}_2\text{O})/\sigma(\text{D}_2\text{O})$	$\sigma_{\text{ion}}(\text{H}_2\text{O})/\sigma_{\text{ion}}(\text{D}_2\text{O})$
800	0.99	1.2
700	1.07	1.36
600	1.23	1.39
500	1.35	1.37
400	1.39	1.41

regions for BaCe_{0.4}Zr_{0.4}Y_{0.2}O_{3-δ} based on the ratio $\sigma(\text{H}_2\text{O})/\sigma(\text{D}_2\text{O})$ as follows:

1) $1.4 < \sigma_{\text{ion}}(\text{H}_2\text{O})/\sigma_{\text{ion}}(\text{D}_2\text{O}) < 1.8$. The oxygen vacancies are fully hydrated and the electrical transfer is almost pure protonic.

2) $1.2 < \sigma_{\text{ion}}(\text{H}_2\text{O})/\sigma_{\text{ion}}(\text{D}_2\text{O}) < 1.4$. Mixed oxygen-ionic and protonic conduction is realized.

3) $\sigma_{\text{ion}}(\text{H}_2\text{O}) \approx \sigma_{\text{ion}}(\text{D}_2\text{O})$. Electric conduction is dominated by oxygen vacancies.

If we apply this for the case of LSS, we can suppose that at the temperatures 500–800 °C the mixed conduction is realized, where the oxygen ionic conductivity is more pronounced at 800 °C, while at temperatures below 600 °C LSS is almost pure proton conductor. However, the clear difference in the ionic conductivity values is observed in the entire temperature range. Therefore, we can suppose that the presence of protons (deuterons) can affect the oxygen ionic conductivity as well. Previously, the possible role of protons in oxygen ionic transport in LaScO₃-based oxides was discussed in [32]. The dependencies in the reductive atmosphere have a nonlinear form and a clear H/D isotope effect is observed over the entire temperature range investigated. The non-linearity of the dependencies

under reductive conditions was previously observed and explained in terms of the mixed conductive nature of LSS and a consequence of the mutual superposition of oxygen and proton conductivities [16]. Moreover, the decrease in the proton concentration with the temperature increase may take place, as it was shown in [33]. Supposing the predominantly ionic conductivity at low $p\text{O}_2$, the electron hole conductivity can be determined as the difference between the conductivity values in air and under reductive conditions. From the obtained dependencies (Figure 3) it can be seen that the electron hole conductivity is almost the same in the temperature range 600–800 °C and slightly decreases in D₂O-humidified atmosphere at the temperatures below 600 °C. The activation energy values of electron hole conductivity were found to be 77 ± 3 and 83 ± 3 kJ/mol for air humidified with H₂O and D₂O respectively.

For more detailed distinguishing of electron hole and ion contributions to the total conductivity, the dependencies of the electrical conductivity on the oxygen partial pressure were measured. The results obtained are presented in Figure 4. Similar to the previously reported dependencies in H₂O-containing atmospheres [30], the electrical conductivity decreases with decreasing oxygen partial pressure and is almost independent of $p\text{O}_2$ at $p\text{O}_2 < 10^{-15}$ atm. Thus, the dependencies were fitted according to

$$\sigma_{\text{tot}} = \sigma_i + \sigma_p^0 \cdot p\text{O}_2^{0.25}, \quad (2)$$

where σ_{tot} is total conductivity, σ_i is ionic conductivity, and σ_p^0 is a value of electron hole conductivity at an oxygen partial pressure of 1 atm.

Using the obtained values of ionic conductivity, transport numbers of ions and electron holes were calculated. Obtained results were compared with previously published values for H₂O-containing atmosphere and are summarized in Figure 5 and Table 2. It can be seen that for all the temperatures the ionic transport numbers in H₂O-containing atmosphere are higher than corresponding values in D₂O-containing one, even at 800 °C, thus confirming the idea of proton influence on oxygen ionic conductivity. With a temperature decrease, this difference increases due to the increasing contribution of proton (deuteron) conductivity. The difference is also observed for different $p\text{O}_2$ values (see Figure 5). Electron hole transport numbers are higher for all the temperatures for a D₂O-containing atmosphere than the corresponding values in a H₂O-containing atmosphere.

Table 2 summarizes the data on transport numbers in air atmospheres, humidified with H₂O and D₂O, available

for other proton-conducting oxides. A similar trend was previously observed for $\text{BaCe}_{0.7}\text{Zr}_{0.1}\text{Y}_{0.1}\text{Yb}_{0.1}\text{O}_{3-\delta}$ (BCZYYb) [34]. This phenomenon is a consequence of the kinetic isotope effect: due to the lower mobility of deuterons the contribution of ionic conductivity decreases, and the contribution of electron hole conductivity increases. For $\text{BaZr}_{0.9}\text{Y}_{0.1}\text{O}_{3-\delta}$ (BZYIO) the opposite trend was observed – the ionic transport

numbers increased and electron hole transport numbers decreased in D_2O containing atmosphere [27]. This was explained by the contribution of a thermodynamic isotope effect. Thus, we can conclude that for LSS under the investigated conditions, the contribution of the thermodynamic isotope effect is not observable and the kinetic isotope effect is responsible for the experimental dependencies, obtained during the study.

Table 2 – Transport numbers of ions and electron holes for LSS in air, humidified with H_2O and D_2O , and available literary data on other proton conducting oxides.

Composition	$T, ^\circ\text{C}$	$t_i(\text{H}_2\text{O})$	$t_{\text{hole}}(\text{H}_2\text{O})$	$t_i(\text{D}_2\text{O})$	$t_{\text{hole}}(\text{D}_2\text{O})$	Source
LSS	800	0.24	0.76	0.20	0.80	This study and [30]
LSS	700	0.34	0.66	0.28	0.72	This study and [30]
LSS	600	0.62	0.38	0.51	0.49	This study and [30]
LSS	500	0.89	0.11	0.76	0.24	This study and [30]
BZYIO	600	0.38	0.62	0.54	0.46	[27]
BCZYYb	800	0.6	0.4	0.56	0.44	[34]
BCZYYb	600	0.89	0.11	0.82	0.18	[34]

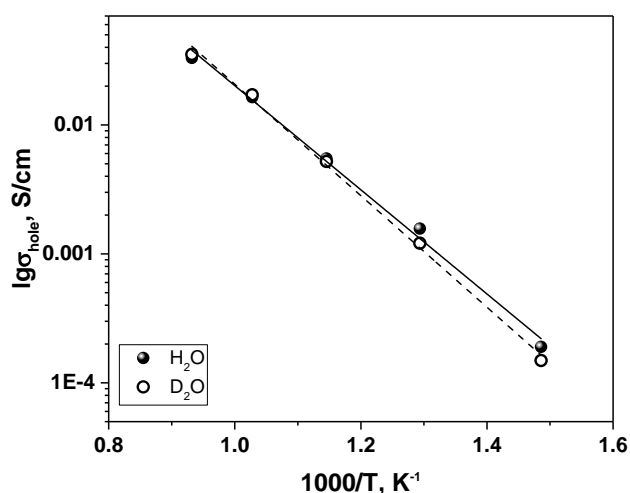


Figure 3 Temperature dependencies of electron hole conductivity for LSS in air, humidified with H_2O and D_2O .

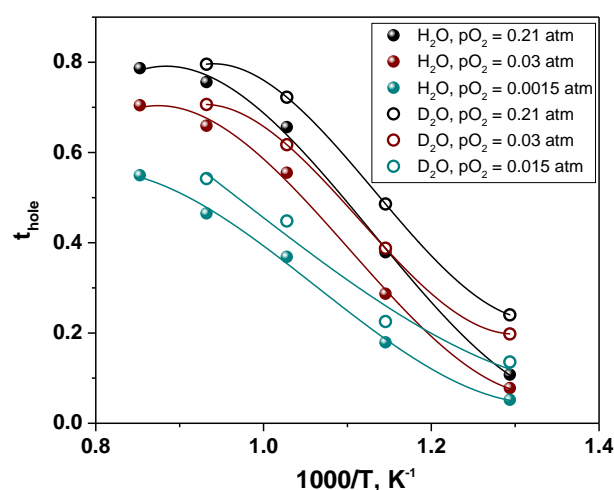


Figure 5 Temperature dependencies of electron hole transport numbers at different $p\text{O}_2$ values. Data for H_2O -containing atmospheres were taken from [30].

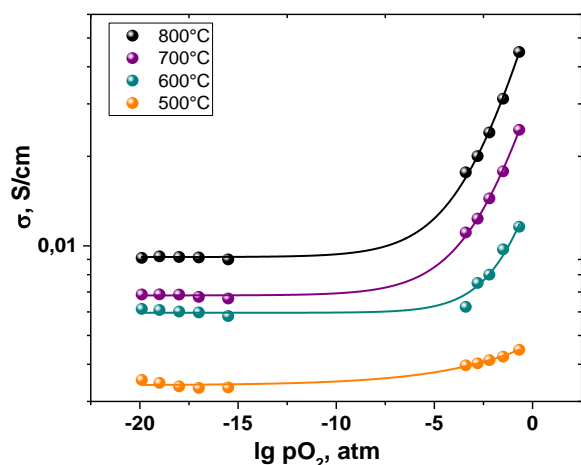


Figure 4 Electrical conductivity of LSS as a function of $p\text{O}_2$ in D_2O -containing atmosphere.

4. Conclusions

During the study, the electrical conductivity of Sr-doped LaScO_3 solid state proton-conducting oxide was investigated by impedance spectroscopy in the atmospheres, humidified with H_2O and D_2O in the temperature range of 400–800 °C and oxygen partial pressure range $10^{-20} < p\text{O}_2 < 0.21$ atm. It was found that under air conditions, replacing H_2O with D_2O did not affect the electrical conductivity at the temperatures 700–800 °C, and led to a decrease in the conductivity at lower temperatures. However, the ionic conductivity values in the D_2O -containing atmosphere were found to be lower than the corresponding values in the H_2O -

containing atmosphere in the entire investigated temperature range, thus, it was suggested that protons (deuterons) influence on the oxygen ionic transport in the investigated oxide. Based on the conductivity dependencies on oxygen partial pressure, the ionic and electron hole contributions to the electrical conductivity were distinguished and corresponding transport numbers were calculated. The kinetic isotope effect, caused by difference in proton and deuteron mobility, was found to be determinative for all investigated conditions: transport numbers of ions decreased with the substitution of H₂O with D₂O, while the electron hole conductivity contribution remained the same.

Supplementary materials

No supplementary materials are available.

Funding

This research had no external funding.

Acknowledgments

The author is grateful to Dr. A.Yu. Stroeva and Dr. A.V. Kuzmin for providing the samples for the studies. The facilities of the shared access center "Composition of Compounds" of IHTe UB RAS were used.

Author contributions

Ekaterina Antonova: Conceptualization; Investigation; Methodology; Writing – Original draft; Writing – Review & Editing; Visualization.

Conflict of interest

The authors declare no conflict of interest.

Additional information

Ekaterina Antonova, PhD, senior researcher, Laboratory of kinetics; Institute of High Temperature Electrochemistry Ural Branch of Russian Academy of Science, Ekaterinburg, Russian Federation; ORCID: [0000-0003-3902-4395](https://orcid.org/0000-0003-3902-4395); Scopus Author ID: [36508426000](https://orcid.org/36508426000).

References

- Jiang X, Yin WJ, High-throughput computational screening of oxide double perovskites for optoelectronic and photocatalysis applications, *J. Energy Chem.*, **57** (2021) 351–358. <https://doi.org/10.1016/j.ijechem.2020.08.046>
- Savchyn VP, Popov AI, Aksimentyeva OI, Klym H, et al., Cathodoluminescence characterization of polystyrene-BaZrO₃ hybrid composites, *Low Temp. Phys.*, **42** (2016) 597–600. <https://doi.org/10.1063/1.4959020>

- Coondoo I, Alikin D, Abramov A, Figueiras FG, et al., Exploring the effect of low concentration of stannum in lead-free BCT-BZT piezoelectric compositions for energy related applications, *J. Alloys Compd.*, **960** (2023) 170562. <https://doi.org/10.1016/j.jallcom.2023.170562>
- Irvine J, Rupp JLM, Liu G, Xu X, et al., Roadmap on inorganic perovskites for energy applications, *J. Phys. Energy*, **3** (2021) 031502. <https://doi.org/10.1088/2515-7655/abff18>
- Golkhatmi SZ, Asghar MI, Lund PD, A review on solid oxide fuel cell durability: latest progress, mechanisms, and study tools, *Renew. Sustain. Energy Rev.*, **161** (2022) 112339. <https://doi.org/10.1016/j.rser.2022.112339>
- Duan C, Huang J, Sullivan N, O'Hayre R, Proton-conducting oxides for energy conversion and storage, *Appl. Phys. Rev.*, **7** (2020) 011314. <https://doi.org/10.1063/1.5135319>
- Kim J, Sengodan S, Kim S, Kwon O, et al., Proton conducting oxides: a review of materials and applications for renewable energy conversion and storage, *Renew. Sust. Energ. Rev.*, **109** (2019) 606–618. <https://doi.org/10.1016/j.rser.2019.04.042>
- Zhang W, Hu YH, Progress in proton-conducting oxides as electrolytes for low-temperature solid oxide fuel cells: From materials to devices, *Energy Sci. Eng.*, **9** (2021) 984–1011. <https://doi.org/10.1002/ese3.886>
- Kreuer KD, Proton-Conducting Oxides, *Annu. Rev. Mater. Res.*, **33** (2003) 333–359. <https://doi.org/10.1146/annurev.matsci.33.022802.091825>
- Rashid NLRM, Samat AA, Jais AA, Somalu MR, et al., Review on zirconate-cerate-based electrolytes for proton-conducting solid oxide fuel cell, *Ceram. Int.*, **46** (2019) 6605–6615. <https://doi.org/10.1016/j.ceramint.2019.01.045>
- Danilov NA, Starostina IA, Starostin GN, Kasyanova AV, et al., Fundamental understanding and applications of protonic Y and Yb-Coped Ba(Ce,Zr)O₃ perovskites: state-of-the-art and perspectives, *Adv. Energy Mater.*, **13** (2023) 2302175. <https://doi.org/10.1002/aenm.202302175>
- Medvedev DA, Lyagaeva JG, Gorbova EV, Demin AK, et al., Advanced materials for SOFC application: Strategies for the development of highly conductive and stable solid oxide proton electrolytes, *Prog. Mat. Sci.*, **75** (2016) 38–79. <https://doi.org/10.1016/j.pmatsci.2015.08.001>
- Zajac W, Rusinek D, Zheng K, Molenda J, Applicability of Gd-doped BaZrO₃, SrZrO₃, BaCeO₃ and SrCeO₃ proton conducting perovskites as electrolytes for solid oxide fuel cells, *Cent. Eur. J. Chem.*, **11** (2013) 471–484. <https://doi.org/10.2478/s11532-012-0144-9>
- Hossain MK, Chanda R, El-Denglawey A, Emrose T, et al., Recent progress in barium zirconate proton conductors for electrochemical hydrogen device applications: A review, *Ceramics Int.*, **47** (2021) 23725–23748. <https://doi.org/10.1016/j.ceramint.2021.05.167>
- Medvedev D, Murashkina A, Pikalova E, Demin A, et al., BaCeO₃: materials development, properties and application, *Prog. Mater. Sci.*, **60** (2014) 72–129. <https://doi.org/10.1016/j.pmatsci.2013.08.001>
- Gorelov VP, Stroeva AY, Solid proton conducting electrolytes based on LaScO₃, *Russ. J. Electrochem.*, **48** (2012) 949–960. <https://doi.org/10.1134/S1023193512100084>
- Nomura K, Takeuchi T, Tanase S, Kageyama H, et al., Proton conduction in (La_{0.9}Sr_{0.1})M^{III}O_{3-δ} (M^{III}=Sc, In, and Lu)

perovskites, *Solid State Ionics*, **154–155** (2002) 647–652. [https://doi.org/10.1016/S0167-2738\(02\)00512-X](https://doi.org/10.1016/S0167-2738(02)00512-X)

18. Kuzmin AV, Stroeve AYu, Gorelov VP, Novikova YuV, et al., Synthesis and characterization of dense proton-conducting $\text{La}_{1-x}\text{Sr}_x\text{ScO}_{3-\alpha}$ ceramics, *Int. J. Hydrog. Energy*, **44** (2019) 1130–1138. <https://doi.org/10.1016/j.ijhydene.2018.11.041>

19. Lybye D, Poulsen FW, Mogensen M, Conductivity of A- and B-site doped LaAlO_3 , LaGaO_3 , LaScO_3 and LaInO_3 perovskites, *Solid State Ionics*, **128** (2000) 91–103. [https://doi.org/10.1016/S0167-2738\(99\)00337-9](https://doi.org/10.1016/S0167-2738(99)00337-9)

20. Stroeve AYu, Gorelov VP, Kuz'min AV, Antonova EP, et al., Phase composition and conductivity of $\text{La}_{1-x}\text{Sr}_x\text{ScO}_{3-\alpha}$ ($x = 0.01–0.20$) under oxidative conditions, *Russ. J. Electrochem.*, **48** (2012) 509–517. <https://doi.org/10.1134/S1023193512050114>

21. Belyakov SA, Lesnichyova AS, Plekhanov MS, Prinz N, et al., Dopant-induced changes of local structures for adjusting the hydration ability of proton conducting lanthanum scandates, *J. Mater. Chem. A*, **11** (2023) 19605–19618. <https://doi.org/10.1039/D3TA03673A>

22. Balakireva VB, Kuz'min AV, Gorelov VP, Ionic conductivity in the $\text{BaZr}_{1-x}\text{Y}_x\text{O}_{3-\delta}$ system ($x = 0.02–0.2$) in $\text{H}_2/\text{H}_2\text{O}$ and $\text{D}_2/\text{D}_2\text{O}$ atmospheres, *Russ. J. Electrochem.*, **46** (2010) 749–753. <https://doi.org/10.1134/S1023193510070050>

23. Hossain MK, Yamamoto T, Hashizume K, Isotopic effect of proton conductivity in barium zirconates for various hydrogen-containing atmospheres, *J. Alloys Compd.*, **903** (2022) 163957. <https://doi.org/10.1016/j.jallcom.2022.163957>

24. Li L, Nino JC, Proton-conducting barium stannates: Doping strategies and transport properties, *Int. J. Hydrogen Energy*, **38** (2013) 1598–1606. <http://dx.doi.org/10.1016/j.ijhydene.2012.11.065>

25. Ananyev MV, Farlenkov AS, Kurumchin EK, Isotopic exchange between hydrogen from the gas phase and proton-conducting oxides: Theory and experiment, *Int. J. Hydrog. Energy*, **43** (2018) 13373–13382. <https://doi.org/10.1016/j.ijhydene.2018.05.150>

26. Tsidilkovski VI, Thermodynamic isotope effect H/D/T in proton-conducting oxides, *Solid State Ionics*, **162–163** (2003) 47–53. [https://doi.org/10.1016/S0167-2738\(03\)00234-0](https://doi.org/10.1016/S0167-2738(03)00234-0)

27. Antonova EP, Yaroslavl'tsev IYu, Bronin DI, Balakireva VB, et al., Peculiarities of electrical transfer and isotopic effects H/D in the proton-conducting oxide $\text{BaZr}_{0.9}\text{Y}_{0.1}\text{O}_{3-\delta}$, *Russ. J. Electrochem.*, **46** (2010) 741–748. <https://doi.org/10.1134/S1023193510070049>

28. Nowick AS, Vaysleyb AV, Isotope effect and proton hopping in high-temperature protonic conductors, *Solid State Ionics*, **97** (1997) 17–26. [https://doi.org/10.1016/S0167-2738\(97\)00081-7](https://doi.org/10.1016/S0167-2738(97)00081-7)

29. Bonanos N, Huijser A, Poulsen FW, H/D isotope effects in high temperature proton conductors, *Solid State Ionics*, **275** (2015) 9–13. <http://dx.doi.org/10.1016/j.ssi.2015.03.028>

30. Farlenkov AS, Putilov LP, Ananyev MV, Antonova EP, et al., Water uptake, ionic and hole transport in $\text{La}_{0.9}\text{Sr}_{0.1}\text{ScO}_{3-\delta}$, *Solid State Ionics*, **306** (2017) 126–136. <https://doi.org/10.1016/j.ssi.2017.04.013>

31. Basbus JF, Arce MD, Napolitano FR, Troiani HE, et al., Revisiting the crystal structure of $\text{BaCe}_{0.4}\text{Zr}_{0.4}\text{Y}_{0.2}\text{O}_{3-\delta}$ proton conducting perovskite and its correlation with transport properties, *ACS Appl. Energy Mater.*, **3** (2020) 2881–2892. <https://dx.doi.org/10.1021/acsaem.9b02498>

32. Stroeve AYu, Gorelov VP, Nature of conductivity of perovskites $\text{La}_{1-x}\text{Sr}_x\text{ScO}_{3-\alpha}$ ($x = 0.01–0.15$) under oxidative and reducing conditions, *Russ. J. Electrochem.*, **48** (2012) 1079–1085. <https://doi.org/10.1134/S1023193512110158>

33. Okuyama Y, Kozai T, Ikeda S, Matsuka M, et al., Incorporation and conduction of proton in Sr-doped LaMO_3 ($M = \text{Al, Sc, In, Yb, Y}$), *Electrichim. Acta*, **125** (2014) 443–449. <https://doi.org/10.1016/j.electacta.2014.01.113>

34. Antonova EP, Gordeev EV, Fedorova KA, Features of electrical transport and H/D isotope effects in the proton-conducting electrolyte $\text{BaCe}_{0.7}\text{Zr}_{0.1}\text{Y}_{0.1}\text{Yb}_{0.1}\text{O}_{3-\delta}$, *Solid State Sciences*, **154** (2024) 107625. <https://doi.org/10.1016/j.solidstatesciences.2024.107625>